

**SLS ISO 6383 PART 1:2021**  
**(ISO 6383-1:2015)**  
**UDC 678.5**

**PLASTICS - FILM AND SHEETING -**  
**DETERMINATION OF TEAR RESISTANCE**  
**PART 1: TROUSER TEAR METHOD**

**SRI LANKA STANDARDS INSTITUTION**



**Sri Lanka Standard**  
**PLASTICS - FILM AND SHEETING - DETERMINATION OF TEAR RESISTANCE**  
**PART 1: TROUSER TEAR METHOD**

**SLS ISO 6383 PART 1:2021**  
**(ISO 6383-1:2015)**

**Gr. C**

*Copyright Reserved*  
**SRI LANKA STANDARDS INSTITUTION**  
**17, Victoria Place**  
**Elvitigala Mawatha**  
**Colombo - 08**  
**Sri Lanka.**

Sri Lanka Standards are subject to periodical revision in order to accommodate the progress made by industry. Suggestions for improvement will be recorded and brought to the notice of the Committees to which the revisions are entrusted.

This Standard does not purport to include all the necessary provisions of a contract

© ISO 2015 - All right reserved.

© SLSI 2021

All right reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the SLSI.

**Sri Lanka Standard**  
**PLASTICS - FILM AND SHEETING - DETERMINATION OF TEAR RESISTANCE**  
**PART 1: TROUSER TEAR METHOD**

**NATIONAL FOREWORD**

This Standard was approved by the Sectoral Committee on Chemical and Polymer Technology and authorized for adoption and publication as a Sri Lanka Standard by the Council of the Sri Lanka Standards Institution on 2021-03-24.

The text of the document **ISO 6383-1:2015** Plastics - film and sheeting - Determination of tear resistance Part 1: Trouser tear method has been accepted for adoption as a Sri Lanka Standard which specifies a method of determining the tear resistance of plastic film or sheet less than 1 mm thick, in the form of standard trouser-shaped test specimens, tested under defined conditions of pre-treatment, temperature, humidity, and speed of testing.

This Standard is identical with **ISO 6383-1:2015** Plastics - film and sheeting - Determination of tear resistance Part 1: Trouser tear method, published by the International Organization for Standardization (ISO).

**TERMINOLOGY AND CONVENTIONS**

The text of the International Standard has been accepted as suitable for publication, without deviation, as a Sri Lanka Standard. However, certain terminology and conventions are not identical with those used in Sri Lanka Standards. Attention is therefore drawn to the following:

- a) Wherever the words “International Standard” appear referring to a particular Standards they should be interpreted as “Sri Lanka Standard”.
  
- b) Wherever page numbers are quoted, they are ISO page numbers.

**CROSS REFERENCES**

**International Standard**

**Corresponding Sri Lanka Standard**

ISO 291, Plastics - Standard atmospheres for conditioning and testing

No corresponding Sri Lanka Standard

ISO 527-3, Plastics - Determination of tensile properties - Part 3: Test conditions for films and sheets

No corresponding Sri Lanka Standard

ISO 4591, Plastics - Film and sheeting - Determination of average thickness of a sample, and average thickness and yield of a roll, by gravimetric techniques (gravimetric thickness)

No corresponding Sri Lanka Standard

ISO 4593, Plastics - Film and sheeting - Determination of thickness by mechanical scanning

SLS 1305 Method of testing for the determination of thickness by mechanical scanning- plastics (film and sheeting)

.....

INTERNATIONAL  
STANDARD

**ISO**  
**6383-1**

Second edition  
2015-12-15

---

---

**Plastics — Film and sheeting —  
Determination of tear resistance —**

**Part 1:  
Trouser tear method**

*Plastiques — Film et feuille — Détermination de la résistance au  
déchirement —*

*Partie 1: Méthode de déchirement pantalon*



Reference number  
ISO 6383-1:2015(E)

© ISO 2015



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org



# Contents

Page

Foreword .....	iv
<b>1</b> <b>Scope</b> .....	<b>1</b>
<b>2</b> <b>Normative references</b> .....	<b>1</b>
<b>3</b> <b>Terms and definitions</b> .....	<b>1</b>
<b>4</b> <b>Significance</b> .....	<b>1</b>
<b>5</b> <b>Principle</b> .....	<b>2</b>
<b>6</b> <b>Apparatus</b> .....	<b>2</b>
<b>7</b> <b>Test specimens</b> .....	<b>2</b>
<b>8</b> <b>Number of test specimens</b> .....	<b>3</b>
<b>9</b> <b>Speed of testing</b> .....	<b>3</b>
<b>10</b> <b>Conditioning</b> .....	<b>3</b>
<b>11</b> <b>Procedure</b> .....	<b>3</b>
<b>12</b> <b>Expression of results</b> .....	<b>3</b>
<b>13</b> <b>Test report</b> .....	<b>4</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#).

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This second edition cancels and replaces the first edition (ISO 6383-1:1983), of which it constitutes a minor revision.

ISO 6383 consists of the following parts, under the general title *Plastics — Film and sheeting — Determination of tear resistance*:

- *Part 1: Trouser tear method*
- *Part 2: Elmendorf method*

# Plastics — Film and sheeting — Determination of tear resistance —

## Part 1: Trouser tear method

### 1 Scope

This part of ISO 6383 specifies a method of determining the tear resistance of plastic film or sheet less than 1 mm thick, in the form of standard trouser-shaped test specimens, tested under defined conditions of pre-treatment, temperature, humidity, and speed of testing.

The method is applicable to film and sheeting of both flexible and rigid materials, provided that the material is not so rigid that brittle fracture occurs during the test, or so deformable, in an irreversible way, that the energy used in the deformation of the specimen legs is significant (i.e. is not negligible) with respect to the energy used in tearing.

The method may not be suitable for determining the tear properties of cellular sheet and film.

### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 527-3, *Plastics — Determination of tensile properties — Part 3: Test conditions for films and sheets*

ISO 4591, *Plastics — Film and sheeting — Determination of average thickness of a sample, and average thickness and yield of a roll, by gravimetric techniques (gravimetric thickness)*

ISO 4593, *Plastics — Film and sheeting — Determination of thickness by mechanical scanning*

### 3 Terms and definitions

For the purpose of this document, the following terms and definitions apply.

#### 3.1

##### **tearing force**

average force required to propagate a tear at a constant tearing speed across a test specimen conforming to [Figure 1](#)

#### 3.2

##### **tear resistance**

tearing force divided by the specimen thickness

### 4 Significance

**4.1** This method may provide data for quality control, acceptance, or rejection in accordance with the terms of specifications and for research and development.

**4.2** Tear properties may vary with specimen preparation, speed of testing, and environment of testing. Consequently, when precise comparative results are required, these factors shall be carefully controlled.

It is possible, in principle, to compare the tear resistance (3.2) of specimens of different materials, provided that their thicknesses do not differ by more than  $\pm 10\%$ . However, caution is necessary in interpreting such results, since the tearing energy can vary considerably with speed of testing for different materials.

## 5 Principle

A rectangular test specimen having a longitudinal slit extending over half its length is subjected to a tensile test on the “trouser legs” formed by the slit. The average force required to tear the specimen completely along its length is used to calculate the tear resistance of the material under test (see [Figure 1](#)).

## 6 Apparatus

**6.1 Tensile testing machine** (not pendulum type), similar to that specified in ISO 527-3, having the following characteristics.

**6.1.1** It shall be power driven and capable of maintaining the appropriate rate of grip separation specified in [Clause 9](#). It is essential that the load measuring device is equipped with an autographic recording device to record the load applied to the specimen as a function of elapsed time from the start of the test.

**6.1.2** The grips shall be equipped with chucks designed to securely hold the legs of the test specimen without slip. The chucks shall be wider than the width of the test specimen and, in order that they remain parallel to each other during a test, they shall not be mounted on swivel joints.

**6.2 Suitable equipment for measuring the thickness** of specimens by the method described in ISO 4593. For embossed film or sheeting, the apparatus specified in ISO 4591 shall be used.

## 7 Test specimens

**7.1** Test specimens shall have the shape and dimensions shown in [Figure 1](#). The length of the slit in the centre of the specimen shall be  $75\text{ mm} \pm 1\text{ mm}$ .

**7.2** The test specimens shall be cut so that the edges are smooth and free from notches. Examination with a low-power microscope is recommended to check freedom from nicks. It is important to pay particular attention to the tip of the slit in the centre of the specimen.

**7.3** The properties of certain types of film and sheeting materials may vary with direction in the plane of the film (anisotropy). In such cases, it is essential to prepare two groups of test specimens with their major axes respectively parallel and perpendicular to the direction of some feature of the film or sheeting which is either visible or inferred from knowledge of the method of its manufacture.

The direction of testing is defined as the direction of the long axis of the test specimen.

With some types of film, different tear resistance results may be obtained for any direction of testing (for example, machine direction or transverse direction) depending, for example, in the case of machine direction test specimens, on whether the tear propagation is in the direction of processing or against the process direction (see [Figure 2](#)). When this is known to occur, two groups of test specimens shall be cut in the direction of testing and slit so that results can be obtained for the two possible directions of tear propagation.

## 8 Number of test specimens

**8.1** A minimum of five test specimens shall be tested in each of the required directions of testing.

**8.2** Specimens which show a tear out of line to the extent that the tear reaches one of the edges of the test specimen shall be discarded and further specimens tested (see [11.3](#)).

## 9 Speed of testing

The speed of testing shall be one of the following:

- 200 mm/min  $\pm$  10 %;
- 250 mm/min  $\pm$  10 %.

**NOTE** At present time, both speeds of testing are common throughout the world. For the time being, both are being allowed for the purpose of this part of ISO 6383. Subsequent revisions of this part of ISO 6383 might only incorporate the testing speed of 200 mm/min.

## 10 Conditioning

Unless otherwise specified, test specimens shall be conditioned and tested in accordance with ISO 291, using atmosphere 23 °C/50 %, except that when a material is known not to be sensitive to humidity, atmosphere 23 °C may be used.

## 11 Procedure

**11.1** Measure the thickness of the material under test using measuring devices complying with the requirements of ISO 4593. If, however, the film is very thin or if it is embossed, determine the thickness by the method of ISO 4591.

**11.1.1** When using measuring devices complying with ISO 4593, measure the thickness of the test specimen at three equidistant points between the tip of the slit and the opposite end of the test specimens. Calculate the mean value.

**11.1.2** When using the method of ISO 4591, the average thickness of the film sample shall be taken as the thickness of the test specimen.

**11.2** Set the initial separation of the grips to 75 mm. Carefully clamp and align the test specimen legs in the grips so that its major axis coincides with an imaginary line joining the centre of the grips (see [Figure 3](#)).

**11.3** Set to the required speed of testing (see [Clause 9](#)), start the machine, and record the load necessary to propagate the tear through the entire un-slit length of the specimen. If the tear deviates from the centre line to such an extent as to reach one of the edges of the specimen, discard the result and test another specimen.

## 12 Expression of results

**12.1** The load-time graph from the autographic recorder of the tensile testing machine will show varying trace forms dependent on the nature of the materials tested and their thickness.

Disregarding the loads recorded in tearing the first 20 mm and the last 5 mm of the un-slit length, determine the approximate mean value of the tearing load over the remaining 50 mm of the un-slit length. When this part of the trace is a wavelike plateau, draw a median line, parallel to the abscissa,

through the wavelike curve (see [Figure 4](#)). Read the load corresponding to this line and record it as the tearing force of the specimen.

**12.2** Calculate the tear resistance of the specimen from Formula (1):

$$\frac{F_t}{d} \quad (1)$$

where

$F_t$  is the tearing force, in newtons, of the specimen;

$d$  is the thickness, in millimetres, of the specimen.

The tearing force may itself be reported, when results are not required to be expressed as the tear resistance.


**12.3** Calculate the arithmetic mean for each set of test specimens.

**12.4** If required, calculate the standard deviation and coefficient of variation for each set of test specimens.

## 13 Test report

The test report shall include the following information:


- a) reference to this part of ISO 6383, i.e. ISO 6383-1;
- b) complete identification of the material tested, including type, source, manufacturer's code, form, and previous history;
- c) thickness of the material tested;
- d) number of specimens tested;
- e) speed of testing;
- f) mean tear resistance and/or tearing force for each direction of testing and tear propagation;
- g) individual test results;
- h) standard atmosphere of ISO 291 used for conditioning and testing and any preconditioning treatment;
- i) standard deviation and coefficient of variation of the test results, if required;
- j) any operational details not specified in this part of ISO 6383 that might have had an influence upon the results.

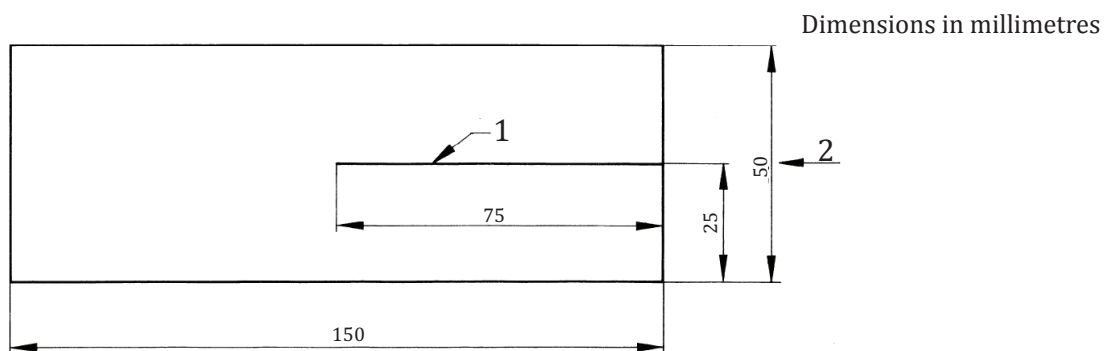

**Key**

- 1 slit
- 2 test direction

**Figure 1 — Test specimen**

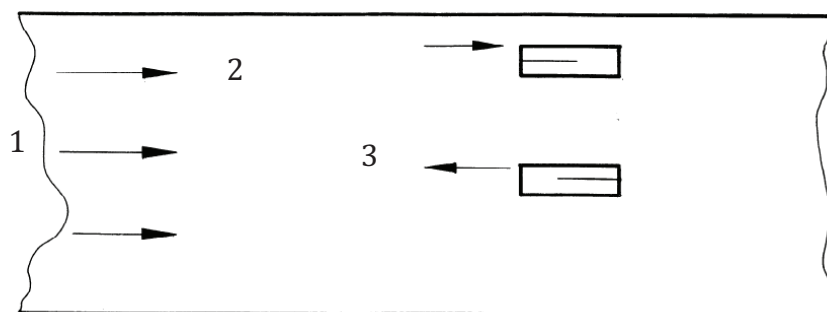

**Key**

- 1 process direction
- 2 tear propagation in process direction
- 3 tear propagation against process direction

**Figure 2 — Direction of tear propagation**


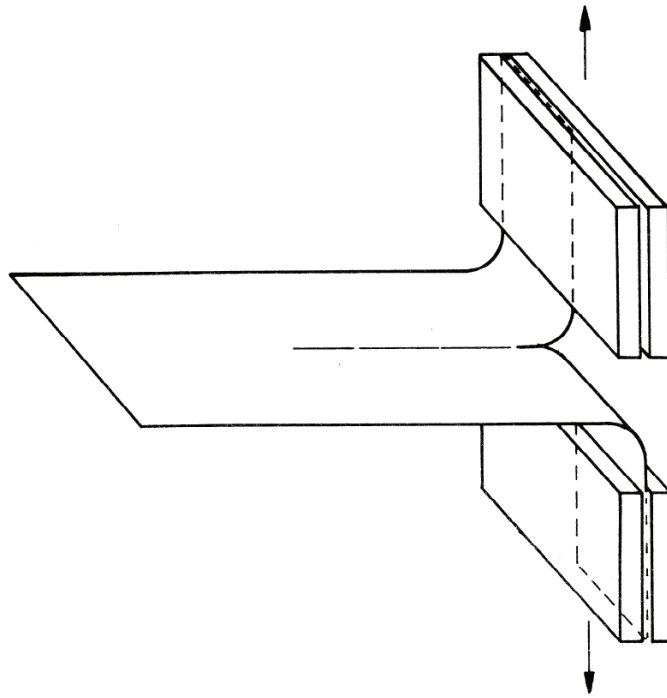


Figure 3 — Method of fixing test specimens in grips

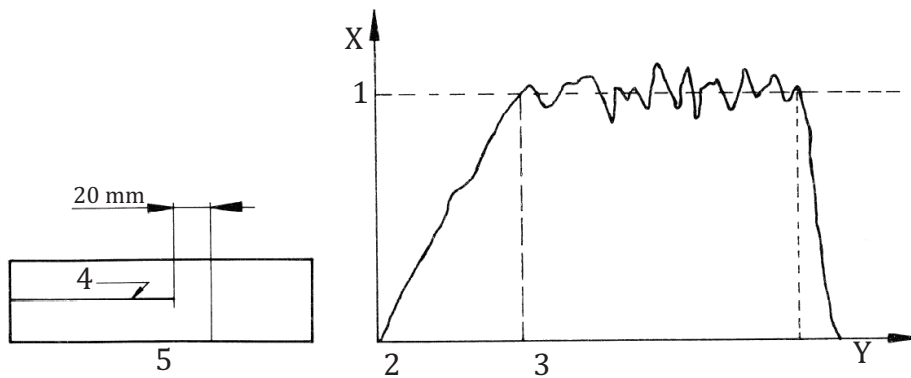

**Key**

- 1 load
- 2 first 20 mm disregarded
- 3 further 50 mm tear
- 4 slit
- 5 marks
- X tearing force
- Y time

Figure 4 — Load-time graph with plateau region








## **SLS CERTIFICATION MARK**

*The Sri Lanka Standards Institution is the owner of the registered certification mark shown below. Beneath the mark, the number of the Sri Lanka Standard relevant to the product is indicated. This mark may be used only by those who have obtained permits under the SLS certification marks scheme. The presence of this mark on or in relation to a product conveys the assurance that they have been produced to comply with the requirements of the relevant Sri Lanka Standard under a well designed system of quality control inspection and testing operated by the manufacturer and supervised by the SLSI which includes surveillance inspection of the factory, testing of both factory and market samples.*

*Further particulars of the terms and conditions of the permit may be obtained from the Sri Lanka Standards Institution, 17, Victoria Place, Elvitigala Mawatha, Colombo 08.*



## SRI LANKA STANDARDS INSTITUTION

The Sri Lanka Standards Institution (SLSI) is the National Standards Organization of Sri Lanka established under the Sri Lanka Standards Institution Act No. 6 of 1984 which repealed and replaced the Bureau of Ceylon Standards Act No. 38 of 1964. The Institution functions under the Ministry of Technology.

The principal objects of the Institution as set out in the Act are to prepare standards and promote their adoption, to provide facilities for examination and testing of products, to operate a Certification Marks Scheme, to certify the quality of products meant for local consumption or exports and to promote standardization and quality control by educational, consultancy and research activity.

The Institution is financed by Government grants, and by the income from the sale of its publications and other services offered for Industry and Business Sector. Financial and administrative control is vested in a Council appointed in accordance with the provisions of the Act.

The development and formulation of National Standards is carried out by Technical Experts and representatives of other interest groups, assisted by the permanent officers of the Institution. These Technical Committees are appointed under the purview of the Sectoral Committees which in turn are appointed by the Council. The Sectoral Committees give the final Technical approval for the Draft National Standards prior to the approval by the Council of the SLSI.

All members of the Technical and Sectoral Committees render their services in an honorary capacity. In this process the Institution endeavours to ensure adequate representation of all view points.

In the International field the Institution represents Sri Lanka in the International Organization for Standardization (ISO), and participates in such fields of standardization as are of special interest to Sri Lanka.