

මෙය රාජ්‍ය භාෂාවෙන් වෙනම මුද්‍රණය කර ඇත

ශ්‍රී ලංකා ප්‍රමිති 355 : 1975
SRI LANKA STANDARD 355 : 1975
විශ්ව දහම වර්ග කිරීම UDC 669.14 : 620.178.7

මානේ සඳහා මාරි ගැටුම්
පරීක්ෂාව (U-අවකිස)

METHOD OF CHARPY IMPACT TEST
(U-NOTCH) FOR STEEL

ලංකා ප්‍රමිති කාර්යාංශය
BUREAU OF CEYLON STANDARDS

METHOD OF CHARPY IMPACT TEST (U-NOTCH) FOR STEEL

SLS 355 : 1975

Gr.3

~~XXXXXXXXXX~~

Copyright Reserved

BUREAU OF CEYLON STANDARDS
53, Dharmapala Mawatha,
Colombo 3.

Sri Lanka Standards are subject to periodical revision in order to accommodate the progress made by industry. Suggestions for improvement will be recorded and brought to the notice of the Committees to which the revisions are entrusted.

This Standard does not purport to include all the necessary provisions of a contract.

BUREAU OF CEYLON STANDARDS
53, Dharmapala Mawatha,
Colombo 3.

Telephone: 26051
26054
26055

Telegrams: "PRAMIKA"

SRI LANKA STANDARD METHOD OF CHARPY IMPACT TEST (U-NOTCH) FOR STEEL

FOREWORD

This Sri Lanka Standard method of Test has been prepared by the Drafting Committee on Steel. It was approved by the Civil Engineering Divisional Committee of the Bureau of Ceylon Standards and was authorised for adoption and publication by the Council of the Bureau on 1975-07-02.

This Standard is one of the Sri Lanka Standards on Methods of Impact Test. The other standard is:-

SLS 354 Izod Impact Test for Steel.

This is based on ISO Recommendation ISO-R 83-Charpy Impact Test (U-Notch) for Steel.

All units given in this standard are in metric units.

1. SCOPE

This Sri Lanka Standard covers the test requirements and procedure of the Charpy Impact Test.

2. PRINCIPLE OF TEST

The test consists in breaking by one blow from a Swinging hammer, under conditions defined hereafter, a test piece U-notched in the middle and supported at each end. The energy absorbed is determined, from which the impact value is obtained.

3. SYMBOLS AND DESIGNATIONS

Number	Symbol	Designation
1	—	Length of test piece
2	a	Thickness of test piece
3	b	Width of test piece
4	—	Thickness of test piece minus depth of notch
5	—	Depth of notch
6	—	Radius of curvature of base of notch
7	L	Distance between supports
8	—	Radius of curvature of supports
9	—	Taper of supports
10	—	Angle at tip of hammer
11	—	Radius of curvature of hammer
12	S_0	Cross-sectional area of test piece below the notch measured in square centimetres before the test
13	KCU	Impact strength with U-notch (key-hole notch) $\frac{\text{Energy absorbed in kgf m}}{S_0}$

4. TEST PIECES

- 4.1 The test piece is machined all over and is 55 mm long and of square section with 10 mm sides. In the centre of the length there is a U-notch (key-hole notch), 5 mm deep (unless otherwise specified), rounded off at the base with a radius of 1 mm.
- 4.2 The plane of symmetry of the notch is perpendicular to the longitudinal axis of the test piece.
- 4.3 The following tolerances on the above dimensions are permitted:

Dimensions in millimetres

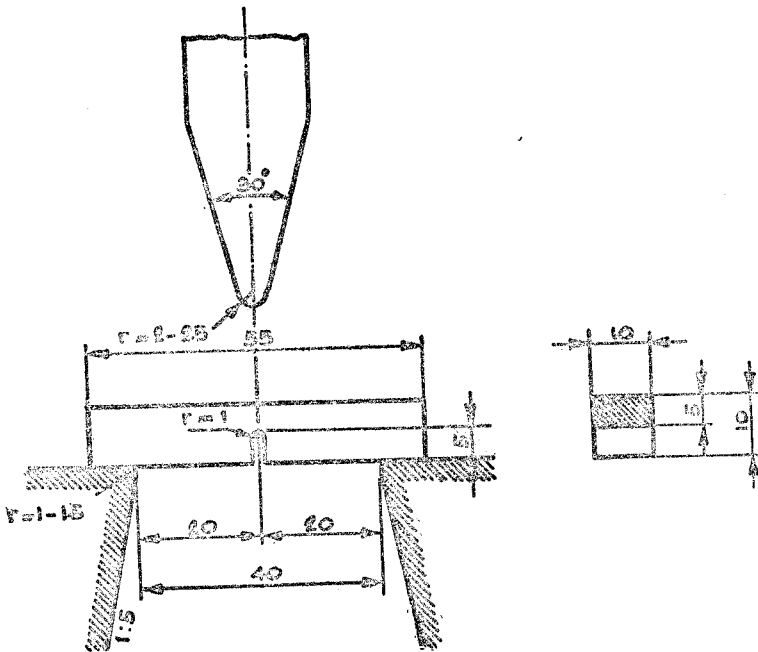
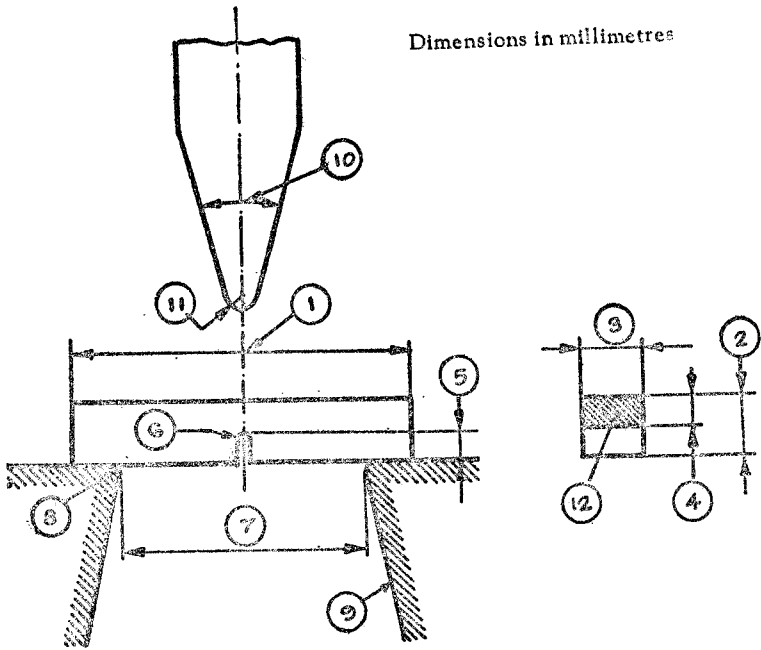


Figure - Charpy impact test (U-notch)

TABLE 1-Tolerances on specified dimensions

Designation	Nominal dimension	Machining Tolerance	
		Values	ISA Symbols
Length	55 mm	± 0.60 mm	j 15
Thickness	10 mm	± 0.11 mm	j 13
Width	10 mm	± 0.11 mm	j 13
Depth of notch	5 mm	± 0.03 mm	j 13
Root radius of notch	1 mm	± 0.07 mm	j 13
Radius of curvature of supports	1 mm		
Taper of supports	1:5		
Angle at tip of hammer	30°	$\pm 1^\circ$	
Distance of notch from ends of test piece	27.5 mm	± 0.42 mm	j 15
Angle between plane of symmetry of notch and longitudinal axis of test piece.	90°	$\pm 2^\circ$	

4.4 The notch may be made by any machine method. The notch should be carefully prepared so that no grooves appear at the base of the notch.

5. TESTING MACHINE

5.1 The testing machine is constructed and installed steady and rigid.

5.1.1 The following conditions should be satisfied:

TABLE 2-Characteristics of testing machine

Designation	Metric units
Distance between supports	40 ± 0.5 mm - 0 mm
Radius of curvature of supports	1 to 1.5 mm
Taper of supports	1:5
Angle at tip of hammer	30°
Radius of curvature of hammer	2 to 2.5 mm
Speed of hammer at the instant of striking	4.5 to 7 m/s

- 5.1.2** The plane of swing of the hammer is vertical. The machine is constructed so that the loss of energy (such as from translation, rotation or vibration) in the machine framework during a test is negligible.
- 5.1.3** The centre of percussion is at the point of impact of the hammer.
- 5.1.4** The accuracy of the graduation of the scale of the machine is ± 0.5 per cent of the maximum striking energy of the machine.
- 5.2** For a standard test the striking energy of the testing machine is 30 ± 1 kgf m. The impact strength obtained under these conditions, using the 5 mm deep U-notch, is denoted by KCU.
- 5.3** Testing machines with different striking energies are permitted in which case the value KCU is supplemented by an index.
- 5.4** The use of U- (key-hole) notches other than the 5 mm deep notch is also denoted by an index.

Example: KCU 10/3 indicates the use of a striking energy of 10 kgf m and a 3 mm deep notch.

KCU 30/3 indicates the use of normal striking energy and a 3 mm deep notch.

6. TEST REQUIREMENTS

- 6.1** The test piece should lie squarely against the supports with the plane of symmetry of the notch within 0.5 mm of the plane midway between them. It should be struck by the hammer in the plane of symmetry of the notch and on the side opposite the notch.
- 6.2** The temperature of the test piece at the moment of breaking should not differ from the specified temperature by more than $\pm 2^{\circ}\text{C}$, unless some other tolerance is agreed. If the temperature of testing is not specified, it is taken as 20°C in temperate climates and 27°C in tropical climates, subject in each case to the above tolerance. In all cases the temperature of test is to be recorded.

SLS 355 : 1975

- 6.3** If, during the test, the test piece is not completely broken, the impact value obtained is indefinite. The test report should state that the test piece was unbroken by $x \text{ kgf m/cm}^2$.

NOTE: There is no general process for converting the impact values, obtained by one method of test, into those which would be obtained by another method of test.

SLS CERTIFICATION MARK

The Sri Lanka Standards Institution is the owner of the registered certification mark shown below. Beneath the mark, the number of the Sri Lanka Standard relevant to the product is indicated. This mark may be used only by those who have obtained permits under the SLS certification marks scheme. The presence of this mark on or in relation to a product conveys the assurance that they have been produced to comply with the requirements of the relevant Sri Lanka Standard under a well designed system of quality control inspection and testing operated by the manufacturer and supervised by the SLSI which includes surveillance inspection of the factory, testing of both factory and market samples.

Further particulars of the terms and conditions of the permit may be obtained from the Sri Lanka Standards Institution, 17, Victoria Place, Elvitigala Mawatha, Colombo 08.



SRI LANKA STANDARDS INSTITUTION

The Sri Lanka Standards Institution (SLSI) is the National Standards Organization of Sri Lanka established under the Sri Lanka Standards Institution Act No. 6 of 1984 which repealed and replaced the Bureau of Ceylon Standards Act No. 38 of 1964. The Institution functions under the Ministry of Science & Technology.

The principal objects of the Institution as set out in the Act are to prepare standards and promote their adoption, to provide facilities for examination and testing of products, to operate a Certification Marks Scheme, to certify the quality of products meant for local consumption or exports and to promote standardization and quality control by educational, consultancy and research activity.

The Institution is financed by Government grants, and by the income from the sale of its publications and other services offered for Industry and Business Sector. Financial and administrative control is vested in a Council appointed in accordance with the provisions of the Act.

The development and formulation of National Standards is carried out by Technical Experts and representatives of other interest groups, assisted by the permanent officers of the Institution. These Technical Committees are appointed under the purview of the Sectoral Committees which in turn are appointed by the Council. The Sectoral Committees give the final Technical approval for the Draft National Standards prior to the approval by the Council of the SLSI.

All members of the Technical and Sectoral Committees render their services in an honorary capacity. In this process the Institution endeavours to ensure adequate representation of all view points.

In the International field the Institution represents Sri Lanka in the International Organization for Standardization (ISO), and participates in such fields of standardization as are of special interest to Sri Lanka.